

Evidence for the FFLO state in CeCoIn₅ from penetration depth measurements

C. Martin,¹ C. C. Agosta,^{1,*} S. W. Tozer,² H. A. Radovan,² E. C. Palm,² T. P. Murphy,² and J. L. Sarrao³

¹*Department of Physics, Clark University, Worcester, MA, 01610*

²*The National High Magnetic Field Laboratory, 1800 E. Paul Dirac Dr., Tallahassee, FL 32310*

³*Los Alamos National Laboratory, Los Alamos, New Mexico 87545*

(Dated: February 2, 2008)

We report penetration depth and resistivity measurements on the heavy fermion superconductor CeCoIn₅ using a self resonant tank circuit based on a tunnel diode oscillator. For magnetic fields applied near parallel to the *ab*-planes and temperatures below 250 mK, two phase transitions were found. The lower field transition, within the superconducting state, is of a second order and we identify it as the transition from the ordinary vortex state to the Fulde, Ferrell, Larkin, Ovchinnikov (FFLO) state. The higher field transition marks the change from the FFLO to the normal state. This higher field transition, H_{c2} , is of first order up to 900 mK, the highest temperature measured. Our normal state resistivity measurements at temperatures between 100 and 900 mK suggest that the FFLO state is related to the change of the quasi-particle interaction strength, F_0^a . Our critical field data for different orientations and temperatures is in good agreement with recent specific heat, magnetization, and resistivity results.

PACS numbers: 74.81.-g, 73.43.Fj, 74.25.Dw, 74.70.Tx

In 1964, Fulde and Ferrell [1] and Larkin and Ovchinnikov [2] predicted that in a purely Pauli limited superconductor, the magnetic field acting on the Cooper pair's spin can induce pairs with nonzero total momentum and, consequently, a spatially modulated order parameter. We have made penetration depth measurements suggesting that this so called FFLO state exists in the heavy fermion superconductor CeCoIn₅.

The FFLO state can lead to an enhancement of the critical field up to 2.5 times the Pauli paramagnetic limit [3]. Gruenberg *et al* [4] showed in 1966 that the FFLO state may exist even in the presence of orbital effects. In the past few years, there has been a growing interest in the theoretical study of this more realistic case, when the critical field is determined by both paramagnetic and orbital effects [5, 6, 7, 8, 9, 10], and special interest in anisotropic (Quasi-2D) [5, 6, 8, 9, 10] and d-wave superconductors [5, 8, 10], which are properties found in CeCoIn₅. The theoretical literature suggests that organics and heavy-fermion superconductors are very promising candidates for observing the FFLO state. In heavy-fermion materials the presence of this state may be even more favorable [9, 11]. Their very low Fermi velocity (large effective mass) decreases the orbital-magnetic field coupling, often ensuring that the system is Pauli limited. However, the first unambiguous experimental evidence for the formation of the FFLO state has been reported only very recently [12] from specific heat and magnetization measurements on CeCoIn₅. More recently, a paper was published by Bianchi *et al.*, that supports this claim [13]. Most of the previous experimental results on CeCoIn₅ ($T_c = 2.3K$) [14] are in good agreement with the theoretical criteria for observing the FFLO state. It has been shown that the orbital pair breaking effect has to be small or completely absent, as measured by the

Maki parameter $\alpha = \sqrt{2} \frac{H_{c2}^0}{H_{Pauli}(0)}$ [15], where H_{c2}^0 is the orbital critical field [16], to favor the FFLO state. This would translate into a value of $\alpha \geq 1.8$ according to Ref. 4, although this calculation was partially based on the BCS theory and may not apply to non s-wave superconductors. This ratio, α , has been calculated by a number of groups [12, 16], but the parameters for this ratio, particularly $H_{Pauli}(0)$, are difficult to measure. From magnetization studies of the critical field [17, 18] it is clear that, when the magnetic field is applied parallel to the *ab*-planes (the *ab*-planes are perpendicular to the [001] direction) at low temperature, H_{c2} is a first order transition, indicating that CeCoIn₅ is in the Pauli limit. We have calculated the Pauli limit for CeCoIn₅ by using a theory-independent method [19, 20], that requires knowledge of Wilson's ratio [21]. The basis of the calculation is that the condensation energy, U_c , is related to both the specific heat via the specific heat jump, and the binding energy of the Cooper pairs via,

$$U_c = \frac{\mu_0}{2} \chi_e H_{Pauli}^2, \quad (1)$$

where χ_e is the Pauli paramagnetic susceptibility. We propose that the jump in the measured specific heat can be integrated from the superconducting transition to zero temperature as an estimate of the condensation energy of the superconducting state, and using the measured susceptibility, H_{Pauli} can be calculated. Although the specific heat leads to a good measure of the condensation energy, the susceptibility measures the Pauli susceptibility plus unwanted terms such as the Landau diamagnetism and inner core electrons. One way to isolate the Pauli susceptibility is to use the Sommerfeld constant γ to estimate χ_e through the use of Wilson's ratio. The difficulty with this method is that the Landé g factor [21] needs to be measured to find Wilson's ratio, and we

are unaware of any direct measurements of g in CeCoIn_5 . However, Won et. al [22] have recently published a critical field calculation, which they fit to critical field data with g as one of the few free parameters. In this paper they found $g = 0.64$ in the parallel orientation and 1.5 in the perpendicular orientation. Using data for γ , ΔC , and $H_{c2}(0)$ ($H_{c2||}^0 = 31.5$ T and $H_{c2\perp}^0 = 12.5$ T.) [12, 14, 17], we calculated the Pauli limit in CeCoIn_5 to be 7.3 T and 4.8 T yielding $\alpha = 6.1$ and 3.7 when B is parallel and perpendicular to the ab -planes, respectively. Higher values of $H_{Pauli}(0)$ can be justified if CeCoIn_5 is not a Fermi Liquid as is discussed below. Lower values of $H_{Pauli}(0)$ are found if χ_e is used directly from recent measurements, which results in unphysical calculated values. These Pauli limits show that with H perpendicular to the ab -planes, where the critical field was found to be 5.0 T, H_{c2} is near the Pauli limit, but in the orientation with H along the ab -planes H_{c2} is above the Pauli limit, consistent with an FFLO state.

The enhancement of the upper critical field in the FFLO state can be particularly substantial for a 2D superconductor [24] and de Haas-van Alphen data on CeCoIn_5 indicate a pronounced quasi-two-dimensional Fermi surface [25, 26]. Specific heat data [23], and thermal conductivity measurements [27], suggest the presence of nodes in the superconducting gap, which is important to characterize the FFLO state [3, 9, 11]. Another requirement for the FFLO state is that the superconductor be in the *clean* limit, $l \gg \xi$, where l is the mean free path of the quasi particles and ξ is the superconducting coherence length. With $l \geq 810$ Å and $\xi \leq 58$ Å based on Refs. 23 and 17, CeCoIn_5 meets this requirement.

In this letter we present tunnel diode oscillator (TDO) measurements on CeCoIn_5 to fields of 18 tesla, at different orientations and temperatures between 60 and 900 mK. The TDO is a self resonant tank circuit where the sample is placed in the coil with the ab planes perpendicular to the ac magnetic field [28]. In this orientation, the penetration depth is measured parallel to the ab planes. Crystal platelets of CeCoIn_5 with approximate dimensions of 1.0 mm dia $\times$ 0.1 mm thick and 0.3 mm dia $\times$ 0.1 mm thick were placed in a 1.33 mm and a 0.35 mm diameter coil, respectively. Details of the sample growth and characterization can be found in Ref. 14. A thermometer was placed on the rotating platform, close to the sample, so that we were able to account for the dc power added by the TDO circuit. The data reported in this letter comes from the large sample where the resonant frequency of the circuit at 80 mK was $\simeq 189$ MHz. The smaller sample and coil at 1.2 GHz yielded similar results. For a TDO experiment, the relative change in the resonant frequency is proportional to the change in the penetration depth ($\frac{\Delta f}{f_0} = \eta \frac{\Delta \lambda}{\lambda_0}$). Obtaining absolute values of the penetration requires a careful calculation of the constant η , which depends on the coil and sample geometries and the demagnetization factor. We did not

calibrate the system for obtaining absolute values, but we measured and subtracted the influence of the background by running the system both with and without the sample, so that the change in the frequency follows accurately the change in penetration depth of only the sample. In the normal state, the penetration is limited by the skin depth ($\delta \propto \sqrt{\rho}$), and we were able to measure the change in resistivity with magnetic field and temperature.

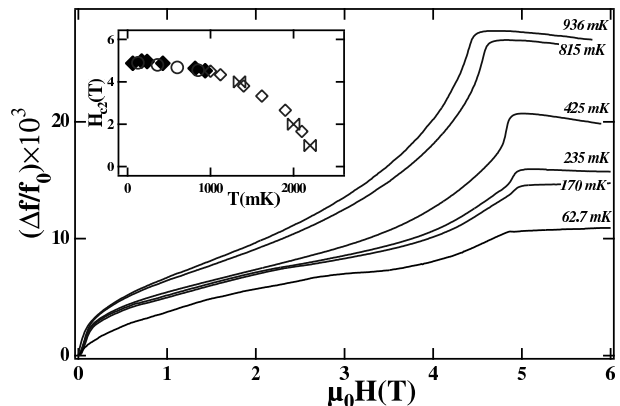


FIG. 1: The relative change in frequency with magnetic field at different temperatures for H perpendicular to the ab planes. The two sweeps above 800 mK do not feature a clear jump in frequency at H_{c2} . The inset displays the H_{c2} vs temperature for this orientation. The filled diamonds represent our data, and the open diamonds, circles and bowties are magnetization data from Ref. [17].

Our phase diagram H - T for the field applied perpendicular to the ab planes is in very good agreement with the magnetization data [17] as is shown in Fig. 1. Analysis of our data shows that this transition changes from first order to second order between 425 and 815 mK, where we no longer observed a sharp jump in the frequency of H_{c2} , which is similar to other experiments [16, 17]. To the lowest temperature measured, we do not see evidence for the FFLO state in the perpendicular direction, although we note that the shape of the 62.7 mK sweep is different than the higher temperature sweeps. We intend to study the low temperature region more carefully in the future.

Figure 2 shows the relative change in frequency with magnetic field when the field is applied parallel to the ab -planes. The background and the subtracted background data are also displayed. As can be seen in Fig. 2, there is a lower field kink, or continuous transition reflected by the change of the slope of the penetration depth versus field, followed by a sharp jump at higher field. We assign the kink, a second order transition, to the ordinary vortex state (VS)-FFLO transition and the upper transition, which is first order, to the FFLO-Normal state transition. This is in very good agreement with the recent observation of FFLO state in CeCoIn_5 by specific heat measurements [12, 13]. Refs. 8, 9 and 11 have

shown theoretically that, unlike originally predicted, the transition at the lower critical field could be of second order, as seen in our data. Above $T \simeq 250$ mK, the second order transition is no longer present. The data shows only the first order phase transition up to the dilution refrigerator limit of 900 mK, as seen in Fig. 2. This first order transition was first predicted by Maki for a type-II superconductor with a large α parameter, below $0.56 T_c$, albeit for the dirty limit [15].

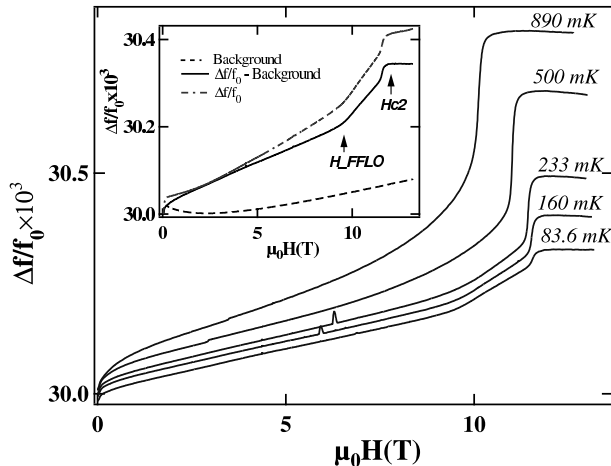


FIG. 2: The relative change in frequency with magnetic field at different temperatures for $H // ab$ planes. The inset shows the raw data at 83.6 mK, the background data, and the data with the background subtracted.

The distinguishing feature of the FFLO state is that the sign of the order parameter alternates spatially, either sinusoidally or more abruptly as the magnetic field approaches the FFLO-normal state phase line [11, 29]. The penetration depth, which is a function of the order parameter [30] ($\lambda \propto \frac{1}{|\psi|}$ and $\propto \frac{1}{\sqrt{n_s}}$), is sensitive to the density of superconducting electrons, n_s . If the order parameter oscillates and is no longer uniform, then the average density of superconducting electrons will be less and the penetration depth will increase. Qualitatively this is the change in our data at the VS-FFLO transition. It is important to mention that the VS-FFLO transition occurs within the superconducting state where resistance measurements, of course, cannot see any signal change.

In Ref. 12 the FFLO state has been observed up to $T \sim 350$ mK and B_{FFLO} is almost 1 T higher than the values we obtain. One possible explanation for the difference in the position of the VS-FFLO transition may be the difference in the quality of the samples, given the strong influence of impurities on the FFLO state. On the other hand, this difference is large, and it may be that the penetration depth and the specific heat measure different aspects of the VS-FFLO phase transition. To try and understand this discrepancy, we have calculated the second derivative of the penetration depth with respect

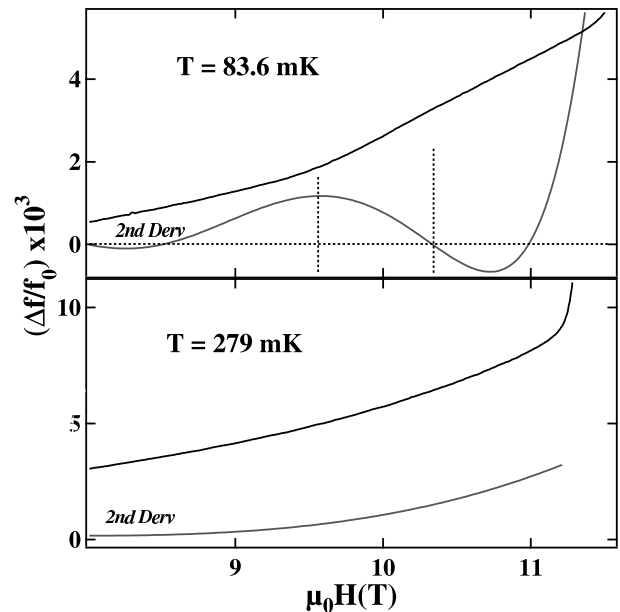


FIG. 3: The second derivative of the penetration with respect to magnetic field for two temperatures in the region around the FFLO transition. The positions of the local maximum and inflection point are marked in the upper region for clarity. At 279 mK, the second derivative is always positive.

to the field, λ'' , and show an example of λ'' in Fig. 3. The first peak in λ'' corresponds to the point of maximum curvature or the obvious kink in the penetration depth measurement near 9.5 T. The second easily identifiable feature in λ'' is where it crosses zero, signifying an inflection point. Although it is unclear exactly how λ'' corresponds to what is physically happening in the FFLO phase transition, the zero of λ'' corresponds to the end of the second order transition as measured by the TDO, and this point matches the transition as measured by specific heat data (see Fig. 4) [12]. Given that λ'' is monotonic and has no zero crossings when the angle is greater than 15° (see Fig. 5) or the temperature is greater than 250 mK, and that the change in the slope of the penetration depth is consistent with an oscillating order parameter, this data provides clear evidence of an FFLO state in CeCoIn₅.

As we have mentioned, the large jump in penetration depth that we associate with the first order upper critical field matches very well with specific heat and data previously obtained by other techniques, as seen in Fig. 4. Yet, as can be seen in Fig. 2, with increasing temperature, the height of the first order transition increases. This increase is due to the change in resistivity of the normal state. By measuring the relative change in frequency with temperature, at a field of $B = 12$ T parallel to the ab planes, we were able to observe the relative change in resistivity in the field-induced normal state (Fig. 6). For temperatures below $T \approx 300$ mK a variable power law

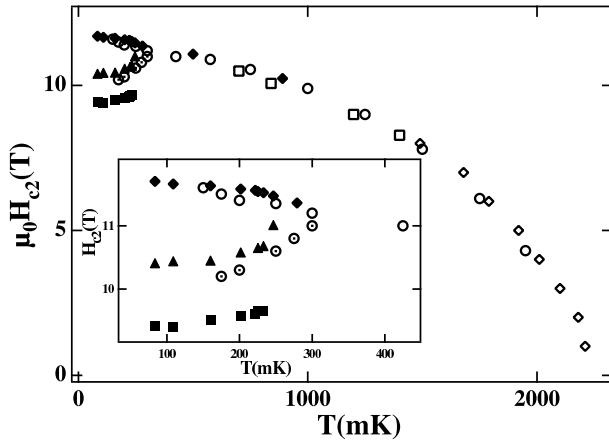


FIG. 4: Critical field as a function of temperature for $H // ab$. The filled symbols represent our data: the upper critical field (diamonds), the FFLO transition from the point of inflection (equilateral triangles) and the FFLO from the position of the *kink*, maximum of second order derivative (squares). Open symbols are data from other studies: specific heat from Ref. [12] (circles and dotted circles) and magnetization [17] (diamonds) and [18] (squares).

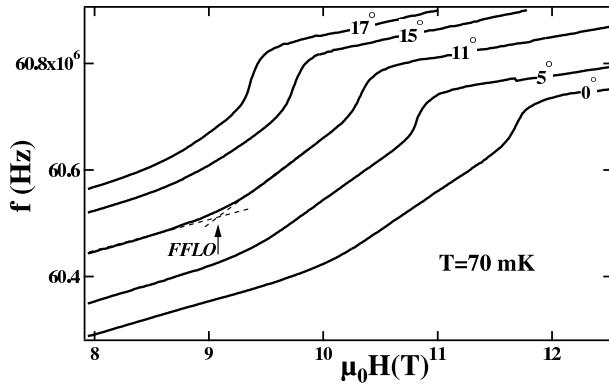


FIG. 5: The penetration depth as a function of magnetic field applied at different angles with respect to the ab planes. The FFLO transition goes away due to increasing orbital effects, however, the superconducting to normal state transition is remains first order, as also was found in Ref. [12, 17].

fit of the data yields a power of 1.92 which is remarkably close to 2, the value expected for Fermi liquid (FL) behavior. In contrast, the two points at higher temperature clearly depart from the power law curve, indicating a change in the behavior of the system to a non Fermi liquid (NFL). We are aware of very recent similar results obtained from a direct measurement of the resistivity [31] and the Sommerfeld constant, γ [32], although at 12 T, Ref. 31 shows the transition to NFL behavior at a higher temperature than what we observed. (We note that other penetration depth studies have also found evidence for NFL behavior, but at zero magnetic field [33, 34]). At 5.5

T with the field perpendicular to the ab planes we only see a linear dependance of the resistivity indicating NFL behavior. This result is consistent with Refs. 31 and 32 where the crossover to FL behavior is observed above 7 T. This change in behavior leads us to believe that the same

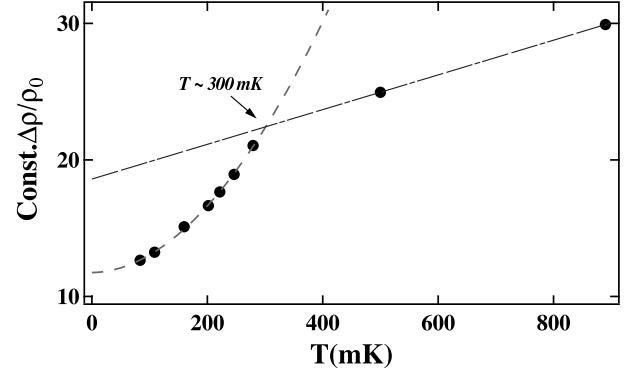


FIG. 6: Change in behavior of the normal state resistivity with temperature at 12 T. The change suggests FL to NFL behavior at the temperature is increased. The lines are power law and linear fits.

parameter may be responsible for the suppression of the FFLO state at higher temperatures *and* for the change in resistivity behavior. The coefficient F_0^a , which measures the interaction strength between quasi-particles, could be this parameter. A larger positive value of F_0^a , and therefore a stronger electron-electron interaction results in a T^2 variation of resistivity with temperature, [35] and at the same time increases the range of stability of the FFLO state by lowering the Pauli paramagnetic susceptibility of the Fermi liquid system ($\chi_e \simeq \frac{\chi_e^0}{(1+F_0^a)}$ where χ_e is the normal fluid susceptibility) [11]. According to Burkhardt [11] as F_0^a becomes smaller, the FFLO state is stable over a smaller temperature and field range and disappears for $F_0^a < -0.5$. It is interesting to note that $(1 + F_0^a)^{-1} = R$, Wilson's ratio. We estimated R to be near 1 based on recent γ and χ_e measurements, although the absolute value of R is unclear because of the problems of isolating the electron paramagnetic susceptibility, as mentioned above. Nevertheless, below $T = 2$ K χ_e is constant and γ increases and thus the trend is for R to decrease, which, consistent with Burkhardt, stabilizes the FFLO state.

We would like to acknowledge R. MacKenzie and N. Fortune for helpful discussions and A. Powell for building some of the electronics. Funding for this project came from the NHMFL In House research and Visiting Scientist programs. The NHMFL is supported by the NSF (Cooperative Agreement DMR-0084173) and the State of Florida.

* Electronic address: cagosta@clarku.edu

- [1] P. Fulde and R. A. Ferrell, Phys. Rev. **135**, A550 (1964).
- [2] A. I. Larkin and Yu. N. Ovchinnikov, Zh. Eksp. Teor. Fiz. **47**, 1136 (1964); or Sov. Phys. JETP **20**, 762 (1965).
- [3] H. Shimahara, J. Phys. Soc. Jpn. **66**, 541 (1997).
- [4] L. W. Gruenberg and L. Gunther, Phys. Rev. Lett. **16** 996 (1966).
- [5] H. Shimahara and D. Rainer, J. Phys. Soc. Jpn. **66**, 3591(1997)
- [6] M. Houzet and A. Buzdin, Europhys. Lett. **50**(3), 375 (2000).
- [7] M. Houzet and A. Buzdin, Phys. Rev. B **63**, 184521 (2001).
- [8] H. Adachi and R. Ikeda, Phys. Rev. B **68**, 184510 (2003).
- [9] A. I. Buzdin and J. P. Brison, Europhys. Lett. **35**, 707 (1996).
- [10] S. Manalo and U. Klein, Phys. Rev. B **65**, 144510 (2002).
- [11] H. Burkhardt and D. Rainer, Ann. Physik **3**, 181 (1994).
- [12] H. A. Radovan, et al., Nature **425**, 51 (2003).
- [13] A. Bianchi et al., Phys. Rev. Lett. **91**, 187004 (2003).
- [14] C. Petrovic et al., J. Phys.: Condens. Matter **13**, L337 (2001).
- [15] K. Maki, Phys. Rev. **148**, 362 (1966).
- [16] A. Bianchi et al., Phys. Rev. Lett. **89**, 137002 (2002).
- [17] T. Tayama et al., Phys. Rev. B **65**, 180504(R) (2002).
- [18] T. P. Murphy et al., Phys. Rev. B **65**, 100514(R) (2002).
- [19] F. Zuo et al., Phys. Rev. B **61**, 750 (2000).
- [20] Detailed calculations to be published C. C. Agosta et al.
- [21] R. H. McKenzie, cond-mat/9905044 v2 (1999).
- [22] H. Won et al., cond-mat/0306548 (2003).
- [23] R. Movshovich et al., Phys. Rev. Lett. **86**, 5152 (2001).
- [24] Bulaevskii L. N., Sov. Phys. JETP **37**, 1133 (1973).
- [25] D. Hall et al., Phys. Rev. B **64**, 212508 (2001).
- [26] R. Settai et al., J. Phys.: Condens. Matter **13**, L627 (2001).
- [27] K. Izawa et al., Phys. Rev. Lett. **87**, 057002 (2001).
- [28] T. Coffey et al., Rev. Sci. Instr. **71**, 4600 (2000).
- [29] A. I. Buzdin and H. Kachkachi, Phys. Lett. A **225**, 341 (1997).
- [30] M. Tinkham, *Introduction to Superconductivity* (McGraw-Hill, NY, 1985).
- [31] J. Paglione, et. al., Phys. Rev. Lett. **91**, 246405 (2003).
- [32] A. Bianchi, et al., Phys. Rev. Lett. **91**, 257001 (2003).
- [33] S. Ozcan et al., Europhys. Lett. **62**, 412 (2003).
- [34] E. Chia et al., Phys. Rev. B **67**, 014527 (2003).
- [35] E. K. U. Gross, et al., *Many Particle Theory*, IOP Publishing (1991).